


STP-PT-028

IMPACT TESTING EXEMPTION CURVES

FOR LOW TEMPERATURE OPERATION
OF PRESSURE PIPING

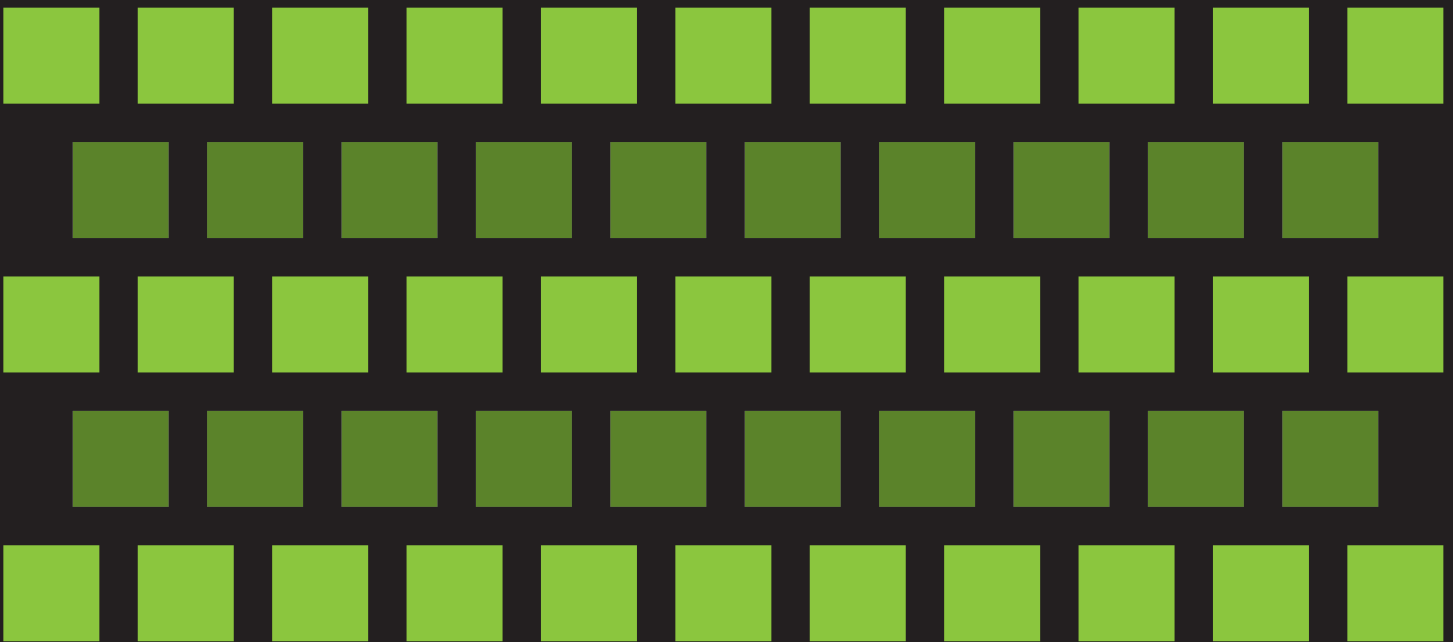

Date of Issuance: January 29, 2009

This report was prepared as an account of work sponsored by ASME Pressure Technologies Codes and Standards and the ASME Standards Technology, LLC (ASME ST-LLC).

Neither ASME, ASME ST-LLC, Pressure Vessel Research Council nor others involved in the preparation or review of this report, nor any of their respective employees, members or persons acting on their behalf, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness or usefulness of any information, apparatus, product or process disclosed, or represents that its use would not infringe upon privately owned rights.

Reference herein to any specific commercial product, process or service by trade name, trademark, manufacturer or otherwise does not necessarily constitute or imply its endorsement, recommendation or favoring by ASME ST-LLC or others involved in the preparation or review of this report, or any agency thereof. The views and opinions of the authors, contributors and reviewers of the report expressed herein do not necessarily reflect those of ASME ST-LLC or others involved in the preparation or review of this report, or any agency thereof.

ASME ST-LLC does not take any position with respect to the validity of any patent rights asserted in connection with any items mentioned in this document, and does not undertake to insure anyone utilizing a publication against liability for infringement of any applicable Letters Patent, nor assumes any such liability. Users of a publication are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, is entirely their own responsibility.

Participation by federal agency representative(s) or person(s) affiliated with industry is not to be interpreted as government or industry endorsement of this publication.

ASME is the registered trademark of the American Society of Mechanical Engineers.

No part of this document may be reproduced in any form,
in an electronic retrieval system or otherwise,
without the prior written permission of the publisher.

ASME Standards Technology, LLC
Three Park Avenue, New York, NY 10016-5990

ISBN No. 978-0-7918-3204-2

Copyright © 2009 by
ASME Standards Technology, LLC
All Rights Reserved

TABLE OF CONTENTS

Foreword	v
Abstract	vi
1 INTRODUCTION	1
2 BACKGROUND	2
3 APPROACH	3
3.1 History and Concepts	3
4 NEW FRACTURE MECHANICS APPROACH TO REQUIRED TOUGHNESS.....	6
4.1 Description of FAD-Based Fracture Mechanics	6
4.2 Reference Flaw Size	6
4.3 Required Material Fracture Toughness	7
5 DERIVATION OF CHARPY V-NOTCH IMPACT TEST REQUIREMENTS	10
5.1 Required Fracture Toughness.....	10
5.2 Lower Shelf Vicinity CVN.....	10
5.3 Upper Shelf Region CVN.....	10
5.4 Transition Region CVN.....	11
5.5 Final CVN Requirement.....	11
5.6 Derivation of Impact Test Exemption Curves for Thin Piping	11
5.7 Derivation of Curves for Reduction in the MDMT Without Impact Testing.....	12
6 CONCLUSION.....	13
Figures.....	15
References	23
Acknowledgments	24
Abbreviations and Acronyms	25
Nomenclature	26

LIST OF FIGURES

Figure 1 - UCS 66 Exemption Curves are Shown. Indicated Notes Define Covered Materials.	15
Figure 2 - Representative Hyperbolic Tangent Fracture Toughness Curve	15
Figure 3 - Implied Dynamic Toughness Curves for Indicated Various Specified Minimum Yield Strength Values	16
Figure 4 - Calculated Exemption Curves Based on Documented Initial Fracture Mechanics Assumptions as Compared with Published Curves	16
Figure 5 - Dependence of Charpy Energy Needed Meet the Toughness Requirement of the Exemption Curve for Indicated Thicknesses as a Function of Loading Rates (Per Second) Shown in the Legend, Ranging from Impact to Static (1E+01/Sec) to Static (1E-05/Sec), for a Material with 38 KSI Specified Minimum Yield Strength.....	17
Figure 6 - The FAD Approach Schematic.....	17

Figure 7 - Modified Hyperbolic Tangent Equation to Provide Uniform Lower Shelf Energy. The Relative Temperature is with Respect to T_0	18
Figure 8 - Example of Charpy Toughness Requirement for As Welded Material for the Case that the Minimum is Set at 20 ft-lbs.....	18
Figure 9 - Pressure Vessel Exemption Curves Calculated for Section VIII, Division 2 for Parts not Subject to PWHT	19
Figure 10 - Exemption Curves for Type A Assigned Materials of Various Possible Yield Strengths	19
Figure 11 - Exemption Curves for Type B Assigned Materials of Various Possible Yield Strengths	20
Figure 12 - Exemption Curves for Type C Assigned Materials of Various Possible Yield Strengths	20
Figure 13 - Exemption Curves for Type D Assigned Materials of Various Possible Yield Strengths	21
Figure 14 - Exemption Curves for Type C Assigned Materials of Various Possible Yield Strengths Where PWHT has been Performed.....	21
Figure 15 - Temperature Reduction Plots for Various Indicated Yield Strengths	22
Figure 16 - Fracture Toughness Expectations Calculated from the Charpy Requirements in ASTM 333 for Steels for Low Temperature Service Using the Procedures Described Herein	22

FOREWORD

This document was developed under a research and development project which resulted from ASME Pressure Technology Codes & Standards (PTCS) committee requests to identify, prioritize and address technology gaps in current or new PTCS Codes, Standards and Guidelines. This project is one of several included for ASME fiscal year 2008 sponsorship which are intended to establish and maintain the technical relevance of ASME codes & standards products. The specific project related to this document is project 07-04 (B31#2), entitled, "Impact Testing Exemption Curves For Low Temperature Operation Of Pressure Piping."

Established in 1880, the American Society of Mechanical Engineers (ASME) is a professional not-for-profit organization with more than 127,000 members promoting the art, science and practice of mechanical and multidisciplinary engineering and allied sciences. ASME develops codes and standards that enhance public safety, and provides lifelong learning and technical exchange opportunities benefiting the engineering and technology community. Visit www.asme.org for more information.

The ASME Standards Technology, LLC (ASME ST-LLC) is a not-for-profit Limited Liability Company, with ASME as the sole member, formed in 2004 to carry out work related to newly commercialized technology. The ASME ST-LLC mission includes meeting the needs of industry and government by providing new standards-related products and services, which advance the application of emerging and newly commercialized science and technology, and providing the research and technology development needed to establish and maintain the technical relevance of codes and standards. Visit www.stllc.asme.org for more information.

ABSTRACT

Extension of ASME exemption curves has been accomplished by consistent application of old and new ASME fracture mechanics concepts originally intended for pressure vessels. It is recognized that materials produced by modern means may be deserving of greater credit for toughness and reassignment to different traditional curves or even new curves may be in order. Where there is impact toughness data, the mean temperature in the transition region may be estimated and new exemption curves developed. Procedures described were used to adjust exemption curves for thickness where pipe wall is less than the normal Charpy specimen width.